Geosynthetic Institute
475 Kedron Avenue
Folsom, PA 19033-1208 USA
TEL (610) 522-8440
FAX (610) 522-8441

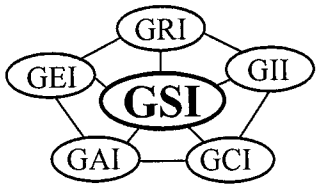

Revision 8: July 10, 2006
Revision schedule on pg. 11

GRI Test Method GM13*

Standard Specification for

"Test Methods, Test Properties and Testing Frequency for
High Density Polyethylene (HDPE) Smooth and Textured Geomembranes"

This specification was developed by the Geosynthetic Research Institute (GRI), with the cooperation of the member organizations for general use by the public. It is completely optional in this regard and can be superseded by other existing or new specifications on the subject matter in whole or in part. Neither GRI, the Geosynthetic Institute, nor any of its related institutes, warrant or indemnifies any materials produced according to this specification either at this time or in the future.

1. Scope

1.1 This specification covers high density polyethylene (HDPE) geomembranes with a formulated sheet density of 0.940 g/ml, or higher, in the thickness range of 0.75 mm (30 mils) to 3.0 mm (120 mils). Both smooth and textured geomembrane surfaces are included.

1.2 This specification sets forth a set of minimum, physical, mechanical and chemical properties that must be met, or exceeded by the geomembrane being manufactured. In a few cases a range is specified.

1.3 In the context of quality systems and management, this specification represents manufacturing quality control (MQC).

Note 1: Manufacturing quality control represents those actions taken by a manufacturer to ensure that the product represents the stated objective and properties set forth in this specification.

1.4 This standard specification is intended to ensure good quality and performance of HDPE geomembranes in general applications, but is possibly not adequate for the complete specification in a specific situation. Additional tests, or more restrictive

*This GRI standard is developed by the Geosynthetic Research Institute through consultation and review by the member organizations. This specification will be reviewed at least every 2-years, or on an as-required basis. In this regard it is subject to change at any time. The most recent revision date is the effective version.

values for test indicated, may be necessary under conditions of a particular application.

Note 2: For information on installation techniques, users of this standard are referred to the geosynthetics literature, which is abundant on the subject.

2. Referenced Documents

2.1 ASTM Standards

D 792 Specific Gravity (Relative Density) and Density of Plastics by Displacement
D 1004 Test Method for Initial Tear Resistance of Plastics Film and Sheeting
D 1238 Test Method for Flow Rates of Thermoplastics by Extrusion Plastometer
D 1505 Test Method for Density of Plastics by the Density-Gradient Technique
D 1603 Test Method for Carbon Black in Olefin Plastics
D 3895 Test Method for Oxidative Induction Time of Polyolefins by Thermal Analysis
D 4218 Test Method for Determination of Carbon Black Content in Polyethylene Compounds by the Muffle-Furnace Technique
D 4833 Test Method for Index Puncture Resistance of Geotextiles, Geomembranes and Related Products
D 5199 Test Method for Measuring Nominal Thickness of Geotextiles and Geomembranes
D 5397 Procedure to Perform a Single Point Notched Constant Tensile Load – (SP-NCTL) Test: Appendix
D 5596 Test Method for Microscopic Evaluation of the Dispersion of Carbon Black in Polyolefin Geosynthetics
D 5721 Practice for Air-Oven Aging of Polyolefin Geomembranes
D 5885 Test method for Oxidative Induction Time of Polyolefin Geosynthetics by High Pressure Differential Scanning Calorimetry
D 5994 Test Method for Measuring the Core Thickness of Textured Geomembranes
D 6693 Test Method for Determining Tensile Properties of Nonreinforced Polyethylene and Nonreinforced Flexible Polypropylene Geomembranes

2.2 GRI Standards

GM10 Specification for the Stress Crack Resistance of Geomembrane Sheet
GM 11 Accelerated Weathering of Geomembranes using a Fluorescent UVA-Condensation Exposure Device
GM 12 Measurement of the Asperity Height of Textured Geomembranes Using a Depth Gage

2.3 U. S. Environmental Protection Agency Technical Guidance Document "Quality Control Assurance and Quality Control for Waste Containment Facilities," EPA/600/R-93/182, September 1993, 305 pgs.

3. Definitions

Manufacturing Quality Control (MQC) - A planned system of inspections that is used to directly monitor and control the manufacture of a material which is factory originated. MQC is normally performed by the manufacturer of geosynthetic materials and is necessary to ensure minimum (or maximum) specified values in the manufactured product. MQC refers to measures taken by the manufacturer to determine compliance with the requirements for materials and workmanship as stated in certification documents and contract specifications.
ref. EPA/600/R-93/182

Manufacturing Quality Assurance (MQA) - A planned system of activities that provides assurance that the materials were constructed as specified in the certification documents and contract specifications. MQA includes manufacturing facility inspections, verifications, audits and evaluation of the raw materials (resins and additives) and geosynthetic products to assess the quality of the manufactured materials. MQA refers to measures taken by the MQA organization to determine if the manufacturer is in compliance with the product certification and contract specifications for the project.
ref. EPA/600/R-93/182

Formulation, n - The mixture of a unique combination of ingredients identified by type, properties and quantity. For HDPE polyethylene geomembranes, a formulation is defined as the exact percentages and types of resin(s), additives and carbon black.

4. Material Classification and Formulation

4.1 This specification covers high density polyethylene geomembranes with a formulated sheet density of 0.940 g/ml, or higher. Density can be measured by ASTM D1505 or ASTM D792. If the latter, Method B is recommended.

4.2 The polyethylene resin from which the geomembrane is made will generally be in the density range of 0.932 g/ml or higher, and have a melt index value per ASTM D1238 of less than 1.0 g/10 min.

4.3 The resin shall be virgin material with no more than 10% rework. If rework is used, it must be a similar HDPE as the parent material.

4.4 No post consumer resin (PCR) of any type shall be added to the formulation.

5. Physical, Mechanical and Chemical Property Requirements

5.1 The geomembrane shall conform to the test property requirements prescribed in Tables 1 and 2. Table 1 is for smooth HDPE geomembranes and Table 2 is for single and double sided textured HDPE geomembranes. Each of the tables are given in English and SI (metric) units. The conversion from English to SI (metric) is soft.

Note 3: The tensile strength properties in this specification were originally based on ASTM D 638 which uses a laboratory testing temperature of 23°C ± 2°C. Since ASTM Committee D35 on Geosynthetics adopted ASTM D 6693 (in place of D 638), this GRI Specification followed accordingly. The difference is that D 6693 uses a testing temperature of 21°C ± 2°C. The numeric values of strength and elongation were not changed in this specification. If a dispute arises in this regard, the original temperature of 23°C ± 2°C should be utilized for testing purposes.

Note 4: There are several tests often included in other HDPE specifications which are omitted from this standard because they are outdated, irrelevant or generate information that is not necessary to evaluate on a routine MQC basis. The following tests have been purposely omitted:

- Volatile Loss
- Dimensional Stability
- Coeff. of Linear Expansion
- Resistance to Soil Burial
- Low Temperature Impact
- ESCR Test (D 1693)
- Wide Width Tensile
- Water Vapor Transmission
- Water Absorption
- Ozone Resistance
- Modulus of Elasticity
- Hydrostatic Resistance
- Tensile Impact
- Field Seam Strength
- Multi-Axial Burst
- Various Toxicity Tests

Note 5: There are several tests which are included in this standard (that are not customarily required in other HDPE specifications) because they are relevant and important in the context of current manufacturing processes. The following tests have been purposely added:

- Oxidative Induction Time
- Oven Aging
- Ultraviolet Resistance
- Asperity Height of Textured Sheet (see Note 6)

Note 6: The minimum average value of asperity height does not represent an expected value of interface shear strength. Shear strength

associated with geomembranes is both site-specific and product-specific and should be determined by direct shear testing using ASTM D5321/ASTM D6243 as prescribed. This testing should be included in the particular site's CQA conformance testing protocol for the geosynthetic materials involved, or formally waived by the Design Engineer, with concurrence from the Owner prior to the deployment of the geosynthetic materials.

Note 7: There are other tests in this standard, focused on a particular property, which are updated to current standards. The following are in this category:

- Thickness of Textured Sheet
- Puncture Resistance
- Stress Crack Resistance
- Carbon Black Dispersion (In the viewing and subsequent quantitative interpretation of ASTM D 5596 only near spherical agglomerates shall be included in the assessment).

Note 8: There are several GRI tests currently included in this standard. Since these topics are not covered in ASTM standards, this is necessary. They are the following:

- UV Fluorescent Light Exposure
- Asperity Height Measurement

5.2 The values listed in the tables of this specification are to be interpreted according to the designated test method. In this respect they are neither minimum average roll values (MARV) nor maximum average roll values (MaxARV).

5.3 The properties of the HDPE geomembrane shall be tested at the minimum frequencies shown in Tables 1 and 2. If the specific manufacturer's quality control guide is more stringent and is certified accordingly, it must be followed in like manner.

Note 9: This specification is focused on manufacturing quality control (MQC). Conformance testing and manufacturing quality assurance (MQA) testing are at the discretion of the purchaser and/or quality assurance engineer, respectively.

6. Workmanship and Appearance

6.1 Smooth geomembrane shall have good appearance qualities. It shall be free from such defects that would affect the specified properties of the geomembrane.

6.2 Textured geomembrane shall generally have uniform texturing appearance. It shall be free from agglomerated texturing material and such defects that would affect the specified properties of the geomembrane.

6.3 General manufacturing procedures shall be performed in accordance with the manufacturer's internal quality control guide and/or documents.

7. MQC Sampling

7.1 Sampling shall be in accordance with the specific test methods listed in Tables 1 and 2. If no sampling protocol is stipulated in the particular test method, then test specimens shall be taken evenly spaced across the entire roll width.

7.2 The number of tests shall be in accordance with the appropriate test methods listed in Tables 1 and 2.

7.3 The average of the test results should be calculated per the particular standard cited and compared to the minimum value listed in these tables, hence the values listed are the minimum average values and are designated as "min. ave."

8. MQC Retest and Rejection

8.1 If the results of any test do not conform to the requirements of this specification, retesting to determine conformance or rejection should be done in accordance with the manufacturing protocol as set forth in the manufacturer's quality manual.

9. Packaging and Marketing

9.1 The geomembrane shall be rolled onto a substantial core or core segments and held firm by dedicated straps/slings, or other suitable means. The rolls must be adequate for safe transportation to the point of delivery, unless otherwise specified in the contract or order.

10. Certification

10.1 Upon request of the purchaser in the contract or order, a manufacturer's certification that the material was manufactured and tested in accordance with this specification, together with a report of the test results, shall be furnished at the time of shipment.

ENGLISH UNITS

Table 1(a) – High Density Polyethylene (HDPE) Geomembrane -Smooth

Properties	Test Method	Test Value							Testing Frequency (minimum)
		30 mils	40 mils	50 mils	60 mils	80 mils	100 mils	120 mils	
Thickness (min. ave.)	D5199	nom.	Nom.	Nom.	Nom.	Nom.	Nom.	Nom.	Per roll
• lowest individual of 10 values		-10%	-10%	-10%	-10%	-10%	-10%	-10%	
Density mg/l (min.)	D 1505/D 792	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	200,000 lb
Tensile Properties *(1)* (min. ave.)	D 6693 Type IV								20,000 lb
• yield strength		63 lb/in.	84 lb/in.	105 lb/in.	126 lb/in.	168 lb/in.	210 lb/in.	252 lb/in.	
• break strength		114 lb/in.	152 lb/in.	190 lb/in.	228 lb/in.	304 lb/in.	380 lb/in.	456 lb/in.	
• yield elongation		12%	12%	12%	12%	12%	12%	12%	
• break elongation		700%	700%	700%	700%	700%	700%	700%	
Tear Resistance (min. ave.)	D 1004	21 lb	28 lb	35 lb	42 lb	56 lb	70 lb	84 lb	45,000 lb
Puncture Resistance (min. ave.)	D 4833	54 lb	72 lb	90 lb	108 lb	144 lb	180 lb	216 lb	45,000 lb
Stress Crack Resistance *(2)*	D5397 (App.)	300 hr.	300 hr.	300 hr.	300 hr.	300 hr.	300 hr.	300 hr.	per GRI-GM10
Carbon Black Content (range)	D 1603 *(3)*	2.0-3.0%	2.0-3.0%	2.0-3.0%	2.0-3.0%	2.0-3.0%	2.0-3.0%	2.0-3.0%	20,000 lb
Carbon Black Dispersion	D 5596	note *(4)*	note *(4)*	note *(4)*	note *(4)*	note *(4)*	note *(4)*	note *(4)*	45,000 lb
Oxidative Induction Time (OIT) (min. ave.) *(5)*									200,000 lb
(a) Standard OIT	D 3895	100 min.	100 min.	100 min.	100 min.	100 min.	100 min.	100 min.	
— or —									
(b) High Pressure OIT	D 5885	400 min.	400 min.	400 min.	400 min.	400 min.	400 min.	400 min.	
Oven Aging at 85°C *(5), (6)*	D 5721								
(a) Standard OIT (min. ave.) - % retained after 90 days	D 3895	55%	55%	55%	55%	55%	55%	55%	per each formulation
— or —									
(b) High Pressure OIT (min. ave.) - % retained after 90 days	D 5885	80%	80%	80%	80%	80%	80%	80%	
UV Resistance *(7)*	GM 11								
(a) Standard OIT (min. ave.)	D 3895	N.R. *(8)*	N.R. *(8)*	N.R. *(8)*	N.R. *(8)*	N.R. *(8)*	N.R. *(8)*	N.R. *(8)*	per each formulation
— or —									
(b) High Pressure OIT (min. ave.) - % retained after 1600 hrs *(9)*	D 5885	50%	50%	50%	50%	50%	50%	50%	

(1) Machine direction (MD) and cross machine direction (XMD) average values should be on the basis of 5 test specimens each direction.
Yield elongation is calculated using a gage length of 1.3 inches
Break elongation is calculated using a gage length of 2.0 in.

(2) The yield stress used to calculate the applied load for the SP-NCTL test should be the manufacturer's mean value via MQC testing.

(3) Other methods such as D 4218 (muffle furnace) or microwave methods are acceptable if an appropriate correlation to D 1603 (tube furnace) can be established.

(4) Carbon black dispersion (only near spherical agglomerates) for 10 different views:
9 in Categories 1 or 2 and 1 in Category 3

(5) The manufacturer has the option to select either one of the OIT methods listed to evaluate the antioxidant content in the geomembrane.

(6) It is also recommended to evaluate samples at 30 and 60 days to compare with the 90 day response.

(7) The condition of the test should be 20 hr. UV cycle at 75°C followed by 4 hr. condensation at 60°C.

(8) Not recommended since the high temperature of the Std-OIT test produces an unrealistic result for some of the antioxidants in the UV exposed samples.

(9) UV resistance is based on percent retained value regardless of the original HP-OIT value.

SI (METRIC) UNITS

Table 1(b) – High Density Polyethylene (HPDE) Geomembrane - Smooth

Properties	Test Method	Test Value							Testing Frequency (minimum)
		0.75 mm	1.00 mm	1.25 mm	1.50 mm	2.00 mm	2.50 mm	3.00 mm	
Thickness - mils (min. ave.) • lowest individual of 10 values	D5199	nom. (mil) -10%	nom. (mil) -10%	nom. (mil) -10%	nom. (mil) -10%	nom. (mil) -10%	nom. (mil) -10%	nom. (mil) -10%	per roll
Density (min.)	D 1505/D 792	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	90,000 kg
Tensile Properties *(1)* (min. ave.) • yield strength • break strength • yield elongation • break elongation	D 6693 Type IV	11 kN/m 20kN/m 12% 700%	15 kN/m 27 kN/m 12% 700%	18 kN/m 33 kN/m 12% 700%	22 kN/m 40 kN/m 12% 700%	29 kN/m 53 kN/m 12% 700%	37 kN/m 67 kN/m 12% 700%	44 kN/m 80 kN/m 12% 700%	9,000 kg
Tear Resistance (min. ave.)	D 1004	93 N	125 N	156 N	187 N	249 N	311 N	374 N	20,000 kg
Puncture Resistance (min. ave.)	D 4833	240 N	320 N	400 N	480 N	640 N	800 N	960 N	20,000 kg
Stress Crack Resistance *(2)*	D 5397 (App.)	300 hr.	300 hr.	300 hr.	300 hr.	300 hr.	300 hr.	300 hr.	per GRI GM-10
Carbon Black Content - %	D 1603 *(3)*	2.0-3.0%	2.0-3.0%	2.0-3.0%	2.0-3.0%	2.0-3.0%	2.0-3.0%	2.0-3.0%	9,000 kg
Carbon Black Dispersion	D 5596	note *(4)*	note *(4)*	note *(4)*	note *(4)*	note *(4)*	note *(4)*	note *(4)*	20,000 kg
Oxidative Induction Time (OIT) (min. ave.) *(5)* (a) Standard OIT — or — (b) High Pressure OIT	D 3895 D 5885	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	90,000 kg
Oven Aging at 85°C *(5), (6)* (a) Standard OIT (min. ave.) - % retained after 90 days — or — (b) High Pressure OIT (min. ave.) - % retained after 90 days	D 5721 D 3895 D 5885	55% 80%	55% 80%	55% 80%	55% 80%	55% 80%	55% 80%	55% 80%	per each formulation
UV Resistance *(7)* (a) Standard OIT (min. ave.) — or — (b) High Pressure OIT (min. ave.) - % retained after 1600 hrs *(9)*	D 3895 D 5885	N. R. *(8)* 50%	N.R. *(8)* 50%	N.R. *(8)* 50%	N.R. *(8)* 50%	N.R. *(8)* 50%	N.R. *(8)* 50%	N.R. *(8)* 50%	per each formulation

(1) Machine direction (MD) and cross machine direction (XMD) average values should be on the basis of 5 test specimens each direction
Yield elongation is calculated using a gage length of 33 mm
Break elongation is calculated using a gage length of 50 mm

(2) The yield stress used to calculate the applied load for the SP-NCTL test should be the manufacturer's mean value via MQC testing.

(3) Other methods such as D 4218 (muffle furnace) or microwave methods are acceptable if an appropriate correlation to D 1603 (tube furnace) can be established.

(4) Carbon black dispersion (only near spherical agglomerates) for 10 different views:
9 in Categories 1 or 2 and 1 in Category 3

(5) The manufacturer has the option to select either one of the OIT methods listed to evaluate the antioxidant content in the geomembrane.

(6) It is also recommended to evaluate samples at 30 and 60 days to compare with the 90 day response.

(7) The condition of the test should be 20 hr. UV cycle at 75°C followed by 4 hr. condensation at 60°C.

(8) Not recommended since the high temperature of the Std-OIT test produces an unrealistic result for some of the antioxidants in the UV exposed samples.

(9) UV resistance is based on percent retained value regardless of the original HP-OIT value.

ENGLISH UNITS

Table 2(a) – High Density Polyethylene (HDPE) Geomembrane - Textured

Properties	Test Method	Test Value							Testing Frequency (minimum)
		30 mils	40 mils	50 mils	60 mils	80 mils	100 mils	120 mils	
Thickness mils (min. ave.) • lowest individual for 8 out of 10 values • lowest individual for any of the 10 values	D 5994	nom. (-5%) -10% -15%	nom. (-5%) -10% -15%	nom. (-5%) -10% -15%	nom. (-5%) -10% -15%	nom. (-5%) -10% -15%	nom. (-5%) -10% -15%	nom. (-5%) -10% -15%	per roll
Asperity Height mils (min. ave.) *(1)*	GM 12	10 mil	10 mil	10 mil	10 mil	10 mil	10 mil	10 mil	every 2nd roll *(2)*
Density (min. ave.)	D 1505/D 792	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	200,000 lb
Tensile Properties (min. ave.) *(3)* • yield strength • break strength • yield elongation • break elongation	D 6693 Type IV	63 lb/in. 45 lb/in. 12% 100%	84 lb/in. 60 lb/in. 12% 100%	105 lb/in. 75 lb/in. 12% 100%	126 lb/in. 90 lb/in. 12% 100%	168 lb/in. 120 lb/in. 12% 100%	210 lb/in. 150 lb/in. 12% 100%	252 lb/in. 180 lb/in. 12% 100%	20,000 lb
Tear Resistance (min. ave.)	D 1004	21 lb	28 lb	35 lb	42 lb	56 lb	70 lb	84 lb	45,000 lb
Puncture Resistance (min. ave.)	D 4833	45 lb	60 lb	75 lb	90 lb	120 lb	150 lb	180 lb	45,000 lb
Stress Crack Resistance *(4)*	D 5397 (App.)	300 hr.	300 hr.	300 hr.	300 hr.	300 hr.	300 hr.	300 hr.	per GRI GM10
Carbon Black Content (range)	D 1603 *(5)*	2.0-3.0 %	2.0-3.0 %	2.0-3.0 %	2.0-3.0 %	2.0-3.0 %	2.0-3.0 %	2.0-3.0 %	20,000 lb
Carbon Black Dispersion	D 5596	note *(6)*	note *(6)*	note *(6)*	note *(6)*	note *(6)*	note *(6)*	note *(6)*	45,000 lb
Oxidative Induction Time (OIT) (min. ave.) *(7)* (a) Standard OIT — or — (b) High Pressure OIT	D 3895 D 5885	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	200,000 lb
Oven Aging at 85°C *(7), (8)* (a) Standard OIT (min. ave.) - % retained after 90 days — or — (b) High Pressure OIT (min. ave.) - % retained after 90 days	D 5721 D 3895 D 5885	55% 80%	55% 80%	55% 80%	55% 80%	55% 80%	55% 80%	55% 80%	per each formulation
UV Resistance *(9)* (a) Standard OIT (min. ave.) — or — (b) High Pressure OIT (min. ave.) - % retained after 1600 hrs *(11)*	GM11 D 3895 D 5885	N.R. *(10)* 50%	N.R. *(10)* 50%	N.R. *(10)* 50%	N.R. *(10)* 50%	N.R. *(10)* 50%	N.R. *(10)* 50%	N.R. *(10)* 50%	per each formulation

(1) Of 10 readings; 8 out of 10 must be ≥ 7 mils, and lowest individual reading must be ≥ 5 mils; also see Note 6.

(2) Alternate the measurement side for double sided textured sheet

(3) Machine direction (MD) and cross machine direction (XMD) average values should be on the basis of 5 test specimens each direction.
Yield elongation is calculated using a gage length of 1.3 inches
Break elongation is calculated using a gage length of 2.0 inches

(4) P-NCTL test is not appropriate for testing geomembranes with textured or irregular rough surfaces. Test should be conducted on smooth edges of textured rolls or on smooth sheets made from the same formulation as being used for the textured sheet materials.
The yield stress used to calculate the applied load for the SP-NCTL test should be the manufacturer's mean value via MQC testing.
The yield stress used to calculate the applied load for the SP-NCTL test should be the manufacturer's mean value via MQC testing.

(5) Other methods such as D 4218 (muffle furnace) or microwave methods are acceptable if an appropriate correlation to D 1603 (tube furnace) can be established.

(6) Carbon black dispersion (only near spherical agglomerates) for 10 different views:
9 in Categories 1 or 2 and 1 in Category 3

(7) The manufacturer has the option to select either one of the OIT methods listed to evaluate the antioxidant content in the geomembrane.

(8) It is also recommended to evaluate samples at 30 and 60 days to compare with the 90 day response.

(9) The condition of the test should be 20 hr. UV cycle at 75°C followed by 4 hr. condensation at 60°C.

(10) Not recommended since the high temperature of the Std-OIT test produces an unrealistic result for some of the antioxidants in the UV exposed samples.

(11) UV resistance is based on percent retained value regardless of the original HP-OIT value.

SI (METRIC UNITS)

Table 2(b) – High Density Polyethylene (HDPE) Geomembrane - Textured

Properties	Test Method	Test Value							Testing Frequency (minimum)
		0.75 mm	1.00 mm	1.25 mm	1.50 mm	2.00 mm	2.50 mm	3.00 mm	
Thickness mils (min. ave.) • lowest individual for 8 out of 10 values • lowest individual for any of the 10 values	D 5994	nom. (-5%) -10% -15%	nom. (-5%) -10% -15%	nom. (-5%) -10% -15%	nom. (-5%) -10% -15%	nom. (-5%) -10% -15%	nom. (-5%) -10% -15%	nom. (-5%) -10% -15%	per roll
Asperity Height mils (min. ave.) *(1)*	GM 12	0.25 mm	0.25 mm	0.25 mm	0.25 mm	0.25 mm	0.25 mm	0.25 mm	every 2nd roll *(2)*
Density (min. ave.)	D 1505/D 792	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	0.940 g/cc	90,000 kg
Tensile Properties (min. ave.) *(3)* • yield strength • break strength • yield elongation • break elongation	D 6693 Type IV	11 kN/m 8 kN/m 12% 100%	15 kN/m 10 kN/m 12% 100%	18 kN/m 13 kN/m 12% 100%	22 kN/m 16 kN/m 12% 100%	29 kN/m 21 kN/m 12% 100%	37 kN/m 26 kN/m 12% 100%	44 kN/m 32 kN/m 12% 100%	9,000 kg
Tear Resistance (min. ave.)	D 1004	93 N	125 N	156 N	187 N	249 N	311 N	374 N	20,000 kg
Puncture Resistance (min. ave.)	D 4833	200N	267 N	333 N	400 N	534 N	667 N	800 N	20,000 kg
Stress Crack Resistance *(4)*	D 5397 (App.)	300 hr.	300 hr.	300 hr.	300 hr.	300 hr.	300 hr.	300 hr.	per GRI GM10
Carbon Black Content (range)	D 1603 *(5)*	2.0-3.0 %	2.0-3.0 %	2.0-3.0 %	2.0-3.0 %	2.0-3.0 %	2.0-3.0 %	2.0-3.0 %	9,000 kg
Carbon Black Dispersion	D 5596	note *(6)*	note *(6)*	note *(6)*	note *(6)*	note *(6)*	note *(6)*	note *(6)*	20,000 kg
Oxidative Induction Time (OIT) (min. ave.) *(7)* (a) Standard OIT — or — (b) High Pressure OIT	D 3895 D 5885	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	100 min. 400 min.	90,000 kg
Oven Aging at 85°C *(7), (8)* (a) Standard OIT (min. ave.) - % retained after 90 days — or — (b) High Pressure OIT (min. ave.) - % retained after 90 days	D 5721 D 3895 D 5885	55% 80%	55% 80%	55% 80%	55% 80%	55% 80%	55% 80%	55% 80%	per each formulation
UV Resistance *(9)* (a) Standard OIT (min. ave.) — or — (b) High Pressure OIT (min. ave.) - % retained after 1600 hrs *(11)*	GM11 D 3895 D 5885	N.R. *(10)* 50%	N.R. *(10)* 50%	N.R. *(10)* 50%	N.R. *(10)* 50%	N.R. *(10)* 50%	N.R. *(10)* 50%	N.R. *(10)* 50%	per each formulation

(1) Of 10 readings; 8 out of 10 must be ≥ 0.18 mm, and lowest individual reading must be ≥ 0.13 mm; also see Note 6.

(2) Alternate the measurement side for double sided textured sheet

(3) Machine direction (MD) and cross machine direction (XMD) average values should be on the basis of 5 test specimens each direction.
Yield elongation is calculated using a gage length of 33 mm
Break elongation is calculated using a gage length of 50 mm

(4) The SP-NCTL test is not appropriate for testing geomembranes with textured or irregular rough surfaces. Test should be conducted on smooth edges of textured rolls or on smooth sheets made from the same formulation as being used for the textured sheet materials.
The yield stress used to calculate the applied load for the SP-NCTL test should be the manufacturer's mean value via MQC testing.

(5) Other methods such as D 4218 (muffle furnace) or microwave methods are acceptable if an appropriate correlation to D 1603 (tube furnace) can be established.

(6) Carbon black dispersion (only near spherical agglomerates) for 10 different views:
9 in Categories 1 or 2 and 1 in Category 3

(7) The manufacturer has the option to select either one of the OIT methods listed to evaluate the antioxidant content in the geomembrane.

(8) It is also recommended to evaluate samples at 30 and 60 days to compare with the 90 day response.

(9) The condition of the test should be 20 hr. UV cycle at 75°C followed by 4 hr. condensation at 60°C.

(10) Not recommended since the high temperature of the Std-OIT test produces an unrealistic result for some of the antioxidants in the UV exposed samples.

(11) UV resistance is based on percent retained value regardless of the original HP-OIT value.

Adoption and Revision Schedule

for

HDPE Specification per GRI-GM13

"Test Methods, Test Properties, Testing Frequency for
High Density Polyethylene (HDPE) Smooth and Textured Geomembranes"

Adopted:	June 17, 1997
Revision 1:	November 20, 1998; changed CB dispersion from allowing 2 views to be in Category 3 to requiring all 10 views to be in Category 1 or 2. Also reduced UV percent retained from 60% to 50%.
Revision 2:	April 29, 1999: added to Note 5 after the listing of Carbon Black Dispersion the following: "(In the viewing and subsequent quantitative interpretation of ASTM D5596 only near spherical agglomerates shall be included in the assessment)" and to Note (4) in the property tables.
Revision 3:	June 28, 2000: added a new Section 5.2 that the numeric table values are neither MARV or MaxARV. They are to be interpreted per the the designated test method.
Revision 4:	December 13, 2000: added one Category 3 is allowed for carbon black dispersion. Also, unified terminology to "strength" and "elongation".
Revision 5:	May 15, 2003: Increased minimum acceptable stress crack resistance time from 200 hrs to 300 hrs.
Revision 6:	June 23, 2003: Adopted ASTM D 6693, in place of ASTM D 638, for tensile strength testing. Also, added Note 2.
Revision 7:	February 20, 2006: Added Note 6 on Asperity Height clarification with respect to shear strength.
Revision 8:	Removed recommended warranty from specification.

Geosynthetic Research Institute
475 Kedron Avenue
Folsom, PA 19033-1208 USA
TEL (610) 522-8440
FAX (610) 522-8441

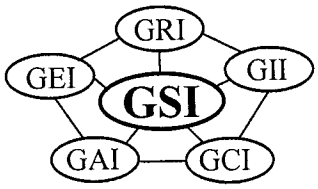

Revision 1: May 15, 2003
Revision schedule is on pg. 12

GRI Test Method GM19*

Standard Specification for

Seam Strength and Related Properties of Thermally Bonded Polyolefin Geomembranes

This specification was developed by the Geosynthetic Research Institute (GRI), with the cooperation of the member organizations for general use by the public. It is completely optional in this regard and can be superseded by other existing or new specifications on the subject matter in whole or in part. Neither GRI, the Geosynthetic Institute, nor any of its related institutes, warrant or indemnifies any materials produced according to this specification either at this time or in the future.

1. Scope

1.1 This specification addresses the required seam strength and related properties of thermally bonded polyolefin geomembranes; in particular, high density polyethylene (HDPE), linear low density polyethylene (LLDPE) and flexible polypropylene both nonreinforced (fPP) and scrim reinforced (fPP-R).

1.2 Numeric values of seam strength and related properties are specified in both shear and peel modes.

Note 1: This specification does not address the test method details or specific testing procedures. It refers to the relevant ASTM test methods where applicable.

1.3 The thermal bonding methods focused upon are hot wedge (single and dual track) and extrusion fillet.

*This GRI standard is developed by the Geosynthetic Research Institute through consultation and review by the member organizations. This specification will be reviewed at least every 2-years, or on an as-required basis. In this regard it is subject to change at any time. The most recent revision date is the effective version.

Note 2: Other acceptable, but less frequently used, methods of seaming are hot air and ultrasonic methods. They are inferred as being a subcategory of hot wedge seaming.

1.4 This specification also suggests the distance between destructive seam samples to be taken in the field, i.e., the sampling interval. However, project-specific conditions will always prevail in this regard.

1.5 This specification is only applicable to laboratory testing.

1.6 This specification does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.

2. Referenced Documents

2.1 ASTM Standards

D751 Standard Test Methods for Coated Fabrics

D6392 Standard Test Method for Determining the Integrity of Nonreinforced Geomembrane Seams Produced Using Thermo-Fusion Methods

2.2 EPA Standards

EPA 600/2.88/052 (NTIS PB-89-129670)
Lining of Waste Containment and Other Containment Facilities

2.3 NSF Standards

NSF International Standard, Flexible Membrane Liners, NSF 54-1993 (depreciated)

2.4 GRI Standards

GM13 Test Properties, Testing Frequency and Recommended Warranty for High Density Polyethylene (HDPE) Smooth and Textured Geomembranes

GM14 Selecting Variable Intervals for Taking Geomembrane Destructive Seam Samples Using the Method of Attributes

GM17 Test Properties, Testing Frequency and Recommended Warranty for Linear Low Density Polyethylene (LLDPE) Smooth and Textured Geomembranes

GM18 Test Properties, Testing Frequency and Recommended Warranty for Flexible Polypropylene (fPP and fPP-R) Geomembranes

3. Definition

3.1 Geomembrane, n – An essentially impermeable geosynthetic composed of one or more synthetic sheets used for the purpose of liquid, gas or solid containment.

3.2 Hot Wedge Seaming – A thermal technique which melts the two opposing geomembrane surfaces to be seamed by running a hot metal wedge or knife between them. Pressure is applied to the top or bottom geomembrane, or both, to form a continuous bond. Seams of this type can be made with dual bond tracks separated by a nonbonded gap. These seams are referred to as dual hot wedge seams or double-track seams.

3.3 Hot Air Seaming – This seaming technique introduces high-temperature air or gas between two geomembrane surfaces to facilitate localized surface melting. Pressure is applied to the top or bottom geomembrane, forcing together the two surfaces to form a continuous bond.

3.4 Ultrasonic Seaming - A thermal technique which melts the two opposing geomembrane surfaces to be seamed by running a ultrasonically vibrated metal wedge or knife between them. Pressure is applied to the top or bottom geomembrane, or both, to form a continuous bond. Some seams of this type are made with dual bond tracks separated by a nonbonded gap. These seams are referred to as dual-track seams or double-track seams.

3.5 Extrusion Fillet Seaming – This seaming technique involves extruding molten resin at the edge of an overlapped geomembrane on another to form a continuous bond. A depreciated method called "extrusion flat" seaming extrudes the molten resin between the two overlapped sheets. In all types of extrusion seaming the surfaces upon which the molten resin is applied must be suitably prepared, usually by a slight grinding or buffing.

4. Significance and Use

4.1 The various methods of field fabrication of seams in polyolefin geomembranes are covered in existing ASTM standards mentioned in the referenced document section. What is not covered in those documents is the numeric values of strength and related properties that the completed seam must meet, or exceed. This specification provides this information insofar as minimum, or maximum, property values are concerned when the field fabricated seams are sampled and laboratory tested in shear and peel. The specification also provides guidance as to what spacing intervals the samples should be taken at typical field installation projects.

5. Sample and Specimen Preparation

5.1 The spacing for taking field seam samples for destructive testing is to be 1 per 500 feet (1 per 150 m) of seam length, or as by directed by the construction quality assurance inspector. As the project continues and data is accumulated, however, this sampling interval should be varied according to the procedure set forth in GRI GM14. Following this procedure three different situations can result.

5.1.1 Good seaming with fewer rejected test results than the preset historic average can result in a sequential increase in the spacing interval, i.e., one per greater than 500 ft. (one per greater than 150 m).

5.1.2 Poor seaming with more rejected test results than the preset historic average can result in a sequential decrease in the spacing interval, i.e., one per less than 500 ft. (one per less than 150 m).

5.1.3 Average seaming with approximately the same test results as the preset historic average will result in the spacing interval remaining the same, i.e., one per 500 ft. (one per 150 m).

Note 3: The method of attributes referred to in GRI GM14 is only one of several statistical strategies that might be used to vary sampling frequency. The use of control charts should also be considered in this regard.

5.2 The size of field seam samples is to be according to the referenced test method, e.g., ASTM D6392 or site-specific CQA plan.

5.3 The individual test specimens taken from the field seam samples are to be tested according to the referenced test method, i.e., ASTM D6392 for HDPE, LLDPE and fPP, and ASTM D751 (as modified by NSF 54) for fPP-R. The specimens are to be conditioned prior to testing according to these same test methods and evaluated accordingly.

6. Assessment of Seam Test Results

6.1 HDPE seams – For HDPE seams (both smooth and textured), the strength of four out of five 1.0 inch (25 mm) wide strip specimens in shear should meet or exceed the values given in Tables 1(a) and 1(b). The fifth must meet or exceed 80% of the given values. In addition, the shear percent elongation, calculated as follows, should exceed the values given in Tables 1(a) and 1(b):

$$E = \frac{L}{L_o}(100) \qquad (1)$$

where

E = elongation (%)
L = extension at end of test (in. or mm)
L_o = original average length (usually 1.0 in. or 25 mm)

Note 4: The assumed gage length is considered to be the unseamed sheet material on either side of the welded area. It generally will be 1.0 in. (25 mm) from the edge of the seam to the grip face.

For HDPE seams (both smooth and textured), the strength of four out of five 1.0 in. (25 mm) wide strip specimens tested in peel should meet or exceed the values given in Tables 1(a) and 1(b). The fifth must meet or exceed 80% of the given values.

In addition, the peel separation (or incursion) should not exceed the values given in Tables 1(a) and 1(b). The value shall be based on the proportion of area of separated bond to the area of the original bonding as follows:

$$S = \frac{A}{A_o}(100) \qquad (2)$$

where

S = separation (%)
A = average area of separation, or incursion (in^2 or mm^2)
A_0 = original bonding area (in^2 or mm^2)

Note 5: The area of peel separation can occur in a number of nonuniform patterns across the seam width. The estimated dimensions of this separated area is visual and must be done with care and concern. The area must not include squeeze-out which is part of the welding process.

Regarding the locus-of-break patterns of the different seaming methods in shear and peel, the following are unacceptable break codes per their description in ASTM D6392 (in this regard, SIP is an acceptable break code);

Hot Wedge: AD and AD-Brk > 25%
Extrusion Fillet: AD1, AD2 and AD-WLD (unless strength is achieved)

6.2 LLDPE seams – For LLDPE seams (both smooth and textured), the strength of four out of five 1.0 in. (25 mm) wide strip specimens in shear should meet or exceed the values given in Table 2(a) and 1(b). The fifth must meet or exceed 80% of the given values. In addition, the shear percent elongation, calculated as follows, should exceed the values given in Tables 2(a) and 2(b).

$$E = \frac{L}{L_o}(100) \qquad (1)$$

where

E = elongation (%)
L = extension at end of test (in. or mm)
L_o = original average length (usually 1.0 in. or 25 mm)

Note 4: The assumed gage length is considered to be the unseamed sheet material on either side of the welded area. It generally

will be 1.0 in. (25 mm) from the edge of the seam to the grip face.

For LLDPE seams (both smooth and textured), the strength of four out of five 1.0 in. (25 mm) wide strip specimens tested in peel should meet or exceed the values given in Tables 2(a) and 2(b). The fifth must meet or exceed 80% of the given values.

In addition, the peel separation (or incursion) should not exceed the values given in Tables 2(a) and 2(b). The value shall be based on the proportion of area of separated bond to the area of the original bonding as follows:

$$S = \frac{A}{A_o}(100) \tag{2}$$

where

S = separation (%)
A = average depth of separation, or incursion (in.^{2} or mm^2)
A_0 = original bonding distance (in.^{2} or mm^2)

Note 5: The area of peel separation can occur in a number of nonuniform patterns across the seam width. The estimated dimensions of this separated area is visual and must be done with care and concern. The area must not include squeeze-out which is part of the welding process.

Regarding the locus-of-break patterns of the different seaming methods in shear and peel, the following are unacceptable break codes per their description in ASTM D6392 (in this regard, SIP is an acceptable break code);

Hot Wedge: AD and AD-Brk > 25%
Extrusion Fillet: AD1, AD2, AD-WLD (unless strength is achieved)

6.3 fPP Seams – For fPP seams (both nonreinforced and scrim reinforced), the strength of four out of five specimens in shear should meet or exceed the values given in Tables 3(a) and 3(b). The fifth must meet or exceed 80% of the given values. Note that the unreinforced specimens are 1.0 in. (25 mm) wide strips and the scrim reinforced specimens are 4.0 in. (100 mm) wide grab tests. In addition, the shear percent elongation on the unreinforced specimens, calculated as follows, should exceed the values given in Tables 3(a) and 3(b).

$$E = \frac{L}{L_o}(100) \tag{1}$$

where
E = elongation (%)
L = extension at end of test (in. or mm)

L_o = original gauge length (usually 1.0 in. or 25 mm)

Note 4: The assumed gage length is considered to be the unseamed sheet material on either side of the welded area. It generally will be 1.0 in. (25 mm) from the edge of the seam to the grip face.

Shear elongation is not relevant to scrim reinforced geomembranes and as such is listed as "not applicable" in Table 3(a) and 3(b).

For fPP seams (both nonreinforced and scrim reinforced), the strength of four out of five specimens in peel should meet or exceed the values given in Tables 3(a) and 3(b). The fifth must meet or exceed 80% of the given values. Note that the unreinforced specimens are 1.0 in. (25 mm) wide strips and the scrim reinforced specimens are grab tests. In addition, the peel percent separation (or incursion) should not exceed the values given in Tables 3(a) and 3(b). The values should be based on the proportion of area of separated bond to the area of the original bonding as follows.

$$S = \frac{A}{A_o}(100) \tag{2}$$

where

S = separation in (%)
A = average depth of separation, or incursion (in.^{2} or mm^2)
A_o = original bonding distance (in.^{2} or mm^2)

Note 5: The area of peel separation can occur in a number of nonuniform patterns across the seam width. The estimated dimensions of this separated area is visual and must be done with care and concern. The area must not include squeeze-out which is part of the welding process.

Regarding the locus-of-break patterns of the different seaming methods in shear and peel, the following are unacceptable break codes per their description in ASTM D6392 (in this regard, SIP is an acceptable break code);

Hot Wedge: AD and AD-Brk > 25%
Extrusion Fillet: AD1, AD2 and AD-WLD (unless strength is achieved)

7. Retest and Rejection

7.1 If the results of the testing of a sample do not conform to the requirements of this specification, retesting to determine conformance or rejection should be done in accordance with the construction quality control or construction quality assurance plan for the particular site under construction.

8. Certification

8.1 Upon request of the construction quality assurance officer or certification engineer, an installer's certification that the geomembrane was installed and tested in accordance with this specification, together with a report of the test results, shall be furnished at the completion of the installation.

PROPOSED REVISED VALUES

Table 1(a) – Seam Strength and Related Properties of Thermally Bonded Smooth and Textured High Density Polyethylene (HDPE) Geomembranes **(English Units)**

Geomembrane Nominal Thickness	30 mils	40 mils	50 mils	60 mils	80 mils	100 mils	120 mils
Hot Wedge Seams[1]							
shear strength[2], lb/in.	57	80	100	120	160	200	240
shear elongation at break[3], %	50	50	50	50	50	50	50
peel strength[2], lb/in.	45	60	76	91	121	151	181
peel separation, %	25	25	25	25	25	25	25
Extrusion Fillet Seams							
shear strength[2], lb/in.	57	80	100	120	160	200	240
shear elongation at break[3], %	50	50	50	50	50	50	50
peel strength[2], lb/in.	45	60	76	91	121	151	181
peel separation, %	25	25	25	25	25	25	25

Notes for Tables 1(a) and 1(b):

1. Also for hot air and ultrasonic seaming methods
2. Value listed for shear and peel strengths are for 4 out of 5 test specimens; the 5th specimen can be as low as 80% of the listed values
3. Elongation measurements should be omitted for field testing

Table 1(b) – Seam Strength and Related Properties of Thermally Bonded Smooth and Textured High Density Polyethylene (HDPE) Geomembranes **(S.I. Units)**

Geomembrane Nominal Thickness	0.75 mm	1.0 mm	1.25 mm	1.5 mm	2.0 mm	2.5 mm	3.0 mm
Hot Wedge Seams[1]							
shear strength[2], N/25 mm.	250	350	438	525	701	876	1050
shear elongation at break[3], %	50	50	50	50	50	50	50
peel strength[2], N/25 mm	197	263	333	398	530	661	793
peel separation, %	25	25	25	25	25	25	25
Extrusion Fillet Seams							
shear strength[2], N/25 mm	250	350	438	525	701	876	1050
shear elongation at break[3], %	50	50	50	50	50	50	50
peel strength[2], N/25 mm	197	263	333	398	530	661	793
peel separation, %	25	25	25	25	25	25	25

PROPOSED REVISED VALUES

Table 2(a) – Seam Strength and Related Properties of Thermally Bonded Smooth and Textured Linear Low Density Polyethylene (LLDPE) Geomembranes **(English Units)**

Geomembrane Nominal Thickness	20 mils	30 mils	40 mils	50 mils	60 mils	80 mils	100 mils	120 mils
Hot Wedge Seams[1]								
shear strength[2], lb/in.	30	45	60	75	90	120	150	180
shear elongation[3], %	50	50	50	50	50	50	50	50
peel strength[2], lb/in.	25	38	50	63	75	100	125	150
peel separation, %	25	25	25	25	25	25	25	25
Extrusion Fillet Seams								
shear strength[2], lb/in.	30	45	60	75	90	120	150	180
shear elongation[3], %	50	50	50	50	50	50	50	50
peel strength[2], lb/in.	25	38	50	63	75	100	125	150
peel separation, %	25	25	25	25	25	25	25	25

Notes for Tables 2(a) and 2(b):

1. Also for hot air and ultrasonic seaming methods
2. Values listed for shear and peel strengths are for 4 out of 5 test specimens; the 5th specimen can be as low as 80% of the listed values
3. Elongation measurements should be omitted for field testing

Table 2(a) – Seam Strength and Related Properties of Thermally Bonded Smooth and Textured Linear Low Density Polyethylene (LLDPE) Geomembranes **(S.I. Units)**

Geomembrane Nominal Thickness	0.50 mm	0.75 mm	1.0 mm	1.25 mm	1.5 mm	2.0 mm	2.5 mm	3.0 mm
Hot Wedge Seams[1]								
shear strength[2], N/25 mm	131	197	263	328	394	525	657	788
shear elongation[3], %	50	50	50	50	50	50	50	50
peel strength[2], N/25 mm	109	166	219	276	328	438	547	657
peel separation, %	25	25	25	25	25	25	25	25
Extrusion Fillet Seams								
shear strength[2], N/25 mm	131	197	263	328	394	525	657	788
shear elongation[3], %	50	50	50	50	50	50	50	50
peel strength[2], N/25 mm	109	166	219	276	328	438	547	657
peel separation, %	25	25	25	25	25	25	25	25

Table 3(a) – Seam Strength and Related Properties of Thermally Bonded Nonreinforced and Reinforced Flexible Polypropylene (fPP) Geomembranes **(English Units)**

Geomembrane Nominal Thickness	30 mil-NR	40 mil-NR	36 mil-R[4]	45 mil-R[4]
Hot Wedge Seams[1]				
shear strength[2], lb/in. (NR); lb (R)	25	30	200	200
shear elongation[3], %	50	50	n/a	n/a
peel strength[2], lb/in. (NR); lb (R)	20	25	20	20
peel separation, %	25	25	n/a	n/a
Extrusion Fillet Seams				
shear strength[2], lb/in. (NR); lb (R)	25	30	200	200
shear elongation[3], %	50	50	n/a	n/a
peel strength[2], lb/in. (NR); lb (R)	20	25	20	20
peel separation, %	25	25	n/a	n/a

Notes for Tables 3(a) and 3(b):

1. Also for hot air and ultrasonic seaming methods
2. Values listed for shear and peel strengths are for 4 out of 5 test specimens; the 5th specimen can be as low as 80% of the listed values
3. Elongation measurements should be omitted for field testing
4. Values are based on grab tensile strength and elongations per D751 for laboratory tested specimens

Table 3(a) – Seam Strength and Related Properties of Thermally Bonded Nonreinforced and Reinforced Flexible Polypropylene (fPP) Geomembranes **(S.I. Units)**

Geomembrane Nominal Thickness	0.75 mm-NR	1.0 mm-NR	0.91 mm-R[4]	1.14 mm-R[4]
Hot Wedge Seams[1]				
shear strength[2], N/25 mm (NR); N (R)	110	130	890	890
shear elongation[3], %	50	50	n/a	n/a
peel strength[2], N/25 mm (NR); N (R)	85	110	90	90
peel separation, %	25	25	n/a	n/a
Extrusion Fillet Seams				
shear strength[2], N/25 mm (NR); N (R)	110	130	890	890
shear elongation[3], %	50	50	n/a	n/a
peel strength[2], N/25 mm (NR); N (R)	85	110	90	90
peel separation, %	25	25	n/a	n/a

Adoption and Revision Schedule

for

Seam Specification per GRI-GM19

"Seam Strength and Related Properties of Thermally Bonded Polyolefin Geomembranes"

Adopted: February 18, 2002

Revision 1: May 15, 2003; Increased selected shear and peel test requirements, per the following:

Material	Test	Seam Type	Current GM19	Proposed GM19	Difference
HDPE	Shear	Hot Wedge	95% yield	95% yield	no change
		Extrusion	95% yield	95% yield	no change
	Peel	Hot Wedge	62% yield	72% yield	16% increase
		Extrusion	62% yield	62% yield	no change
LLDPE	Shear	Hot Wedge	1300 psi break	1500 psi break	15% increase
		Extrusion	1300 psi break	1500 psi break	15% increase
	Peel	Hot Wedge	1100 psi break	1250 psi break	14% increase
		Extrusion	1100 psi break	1100 psi break	no change